

^{23}Na NMR Studies of Non-superconducting and Superconducting $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ ($T_c < 1.8$ and ~ 4.5 K)

H. Ohta, Y. Itoh, C. Michioka and K. Yoshimura
Department of Chemistry, Graduate School of Science,
Kyoto University, Kyoto 606-8502, Japan
(February 2, 2008)

We report ^{23}Na NMR studies of the polycrystalline samples of *bilayer* hydrated cobalt oxides $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ with the superconducting transition temperatures $T_c < 1.8$ and ~ 4.5 K. The magnitude of the ^{23}Na nuclear spin-lattice relaxation rate $1/T_1$ significantly decreased from non-hydrated $\text{Na}_{0.7}\text{CoO}_2$ to the *bilayer* hydrates. We found that the temperature dependence of $1/T_1$ of the non-superconducting *bilayer* hydrate is similar to that of the non-hydrated $\text{Na}_{0.7}\text{CoO}_2$, the spin dynamics of which is understood by *A*-type (intra-layer ferromagnetic and inter-layer antiferromagnetic) spin fluctuations. The superconducting phase is located close to the *A*-type magnetic instability.

74.25.Nf, 74.70.-b, 76.60.-k

The discovery of *bilayer* hydrated cobalt oxide superconductor $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$ [1] has provided us with a new opportunity to study the itinerant electron magnetism on a triangular lattice. Spin frustration effect on a triangular lattice has long been expected to realize the resonating valence bond, so-called RVB state [2,3], and the strong thermoelectric power of the parent Na_xCoO_2 has attracted much interests in the vital roles of charge fluctuations of $\text{Co}^{3+}/\text{Co}^{4+}$ [4] and of the spin entropy. At first, the effect of water intercalation on superconductivity was thought only to extend the interlayer distance between the CoO_2 layers, but now it turns out that the diversity of the site occupation of Na ions [5,6] and H_3O^+ oxonium ions [7] gives a variety of electronic states of *bilayer* hydrated cobalt oxides. Although the Na ions surrounded by the intercalated water molecules are the key ingredients for occurrence of superconductivity, their electronic effects on the CoO_2 planes are poorly understood.

The parent non-hydrate $\text{Na}_{0.7}\text{CoO}_2$ has an itinerant electronic system. Inelastic neutron scattering studies revealed the *A*-type spin fluctuations on the CoO_2 planes, i.e. intra-plane ferromagnetic and inter-plane antiferromagnetic instability at low temperatures [8]. The temperature and magnetic-field dependence of electrical resistivity shows characteristic of a magnetic quantum critical point [9]. The ^{23}Na nuclear spin-lattice relaxation time indicates the existence of two dimensional ferromagnetic spin fluctuations at low temperatures [10] and of charge fluctuations or the motion of Na ions at high temperatures [11]. The detail analysis of ^{23}Na NMR spectra

revealed the vital role of charge degree of freedom [12].

A non-superconducting *bilayer* hydrate cobalt oxide, $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$, was reported to exhibit a small internal magnetic field [13]. The weak magnetic behavior suggests a close interplay between the occurrence of superconductivity and magnetic instability. The delicate amounts of Na ions, water molecules, and oxonium ions may control the carrier doping level of the CoO_2 planes. However, no chemical treatment to synthesize the non-superconductors has been established so far for the *bilayer* hydrates.

Recently, we found successful synthesis method of the non-superconducting *bilayer* hydrate with $T_c < 1.8$ K and the derivative superconducting hydrate with $T_c \sim 4.5$ K with a small upper critical field H_{c2} . In this Letter, we report ^{23}Na NMR studies for the non-superconducting and the derivative superconducting *bilayer* hydrates. We observed that the Na nuclear spin-lattice relaxation rate $1/T_1$ of the non-superconducting *bilayer* hydrate is of two order smaller than that of the parent $\text{Na}_{0.7}\text{CoO}_2$ but shows the similar temperature dependence. The electronic state of the non-superconducting *bilayer* hydrate is found to be nearly the same as that of the parent $\text{Na}_{0.7}\text{CoO}_2$, i.e. the *A*-type spin fluctuations on the CoO_2 planes at low temperatures and charge fluctuations/the motion of Na ions at high temperatures.

The parent compound, $\text{Na}_{0.7}\text{CoO}_2$ was synthesized by a conventional solid-state reaction. The powder of $\text{Na}_{0.7}\text{CoO}_2$ was immersed in $\text{Br}_2/\text{CH}_3\text{CN}$ solution for 1 day for deintercalation of Na^+ . The powder was immersed in distilled water for 1 day to intercalate H_2O molecules. After filtering the powder, the sample was put into a chamber with an atmosphere of 75 % humidity air. Recently we have investigated the duration (keeping time in the humidity-controlled chamber) dependence of the physical properties of *bilayer* hydrates [14]. The sample shows a systematic change in the chamber as a function of the duration day by day. After each duration, cryopreservation at -10°C was found to be effective to quench further change of the sample. The duration effect appears especially in the superconductivity, i.e. the superconducting transition temperature T_c and the volume fraction. In addition, the duration effect was found to be sensitive to the initial condition of the powder and the atmosphere in the chamber.

In this study we prepared two samples. The duration

of the sample named BLH1 is 1 week, and that of BLH2 is 1 month. Figure 1 shows the temperature dependence of the magnetic susceptibility under $H = 20$ Oe measured by a SQUID magnetometer. T_c of BLH2 is 4.5 K while no signs of the superconductivity appear down to 1.8 K in BLH1. Any samples with short duration do not show superconductivity down to 1.8 K, and then BLH1 is classified into these non-superconducting bilayer hydrates. The present BLH2 has a smaller upper critical field H_{c2} than that reported in Ref. [15]. Zero-field ^{59}Co nuclear quadrupole resonance (NQR) experiments have also been performed to characterize the samples. For BLH1, the appearance of an internal magnetic field below about 4.5 K was observed in a broad ^{59}Co NQR spectrum, being similar to the previous report [13]. For BLH2, the superconducting transition was confirmed by the rapid decrease of the ^{59}Co nuclear spin-lattice relaxation rate $1/^{59}T_1$. The details of the results will be reported elsewhere.

The ^{23}Na (spin $I=3/2$) NMR experiments have been carried out by a coherent-type pulsed NMR spectrometer for the powdered samples. The ^{23}Na NMR frequency spectra were obtained by a fast Fourier transformation (FFT) technique for the free induction signals. The ^{23}Na nuclear spin-lattice relaxation time $^{23}T_1$ was measured by an inversion recovery technique. The free induction signal $M(t)$ as a function of a duration time t after an inversion pulse and $M(\infty)[\equiv M(t > 10T_1)]$ were recorded. In order to estimate $^{23}T_1$, the recovery curves $p(t) \equiv 1 - M(t)/M(\infty)$ were fit to the data by $p(t) = p(0)[0.1e^{-6t/T_1} + 0.9e^{-3t/T_1}]$ for central transition ($I_z=1/2 \leftrightarrow 1/2$), where $p(0)$ and T_1 are fit parameters.

Figure 2 shows the FFT ^{23}Na NMR spectra of the parent $\text{Na}_{0.7}\text{CoO}_2$, the bilayer hydrated BLH1 and BLH2. For Na_xCoO_2 , there are two crystallographic Na sites, Na1 and Na2, which reside just above the Co site and in the center of the Co triangles, respectively. The two ^{23}Na NMR lines in Na_xCoO_2 in Fig. 2 are assigned to the central transition lines ($I_z=1/2 \leftrightarrow -1/2$) of Na1 and Na2 nuclei [12]. They are affected by finite Knight shift and electric quadrupole shift, which is consistent with Ref. [12]. For the bilayer hydrates, the single sharp lines with small Knight shift are observed, being similar to the result for $\text{Na}_{0.35}\text{CoO}_2$ (sodium deintercalated non-hydrate compound) in Ref. [12]. The hydration diminishes the Co-to-Na hyperfine coupling and shields the electric field gradient from the charge distribution on the CoO_2 planes. The ^{23}Na NMR spectra and nuclear spin-lattice relaxation studies (shown below) revealed the electric and magnetic shielding effect by water intercalation.

Figure 3 shows typical ^{23}Na nuclear spin-lattice relaxation curves (recovery curves) for bilayer hydrated BLH1 and BLH2 at 50 K. The solid curves are the least-squares fits by the theoretical function for central transition lines ($I_z=1/2 \leftrightarrow 1/2$) mentioned above. Non-single exponential relaxation was observed in all the recovery curves.

Since neither appreciable split nor asymmetric profile due to the electric quadrupole shift was observed in the present ^{23}Na NMR spectra in Fig. 2, then we assumed that the satellite lines of $I_z=\pm 3/2 \leftrightarrow \pm 1/2$ are wiped out. Thus, we determined the values of $^{23}T_1$ from these fits. In passing, we have already analyzed the data by a stretched exponential function based on an impurity-induced NMR relaxation theory [16]. We confirmed that the present results on T_1 are independent of the details of analysis.

Figure 4(a) shows the temperature dependence of the ^{23}Na nuclear spin-lattice relaxation rate $1/^{23}T_1$ for BLH1 and BLH2. For comparison, the temperature dependence of the ^{59}Co nuclear spin-lattice relaxation rate $1/^{59}T_1$ for BLH1 and BLH2 are shown in Fig. 4(b). Since all the $1/^{23}T_1$ seem to reach zero at $T=0$ K in Fig. 4(a), no paramagnetic impurity causes the ^{23}Na NMR relaxation. The behavior of $1/^{23}T_1$ in Fig. 4(a) can be considered to be intrinsic. The magnitude of $1/^{23}T_1$ significantly decreases from BLH1 ($T_c < 1.8$ K) to BLH2 ($T_c=4.5$ K), whereas that of $1/^{59}T_1$ at low temperatures does not change so much. The broad maxima of $1/^{23}T_1$, denoted by T^* , are seen in Fig. 4(a), whereas $1/^{59}T_1$ is not in Fig. 4(b). We suppose that the different T_c results from the difference in the degree of hydration. Thus, the difference in spin dynamics at the Na site indicates the difference in shielding effect. The different temperature dependence of $1/^{23}T_1$ and $1/^{59}T_1$ indicates the existence of another fluctuation mode at the Na site between the CoO_2 planes, in addition to transferred fluctuations from the in-plane electron spin fluctuations. The in-plane spin fluctuations probed by $1/^{59}T_1$ is nearly independent of T_c 's, whereas an interplane fluctuations probed by $1/^{23}T_1$ is strongly dependent on T_c 's. Thus, an interlayer coupling probed by the Na NMR $^{23}T_1$ may control the value of T_c .

For the non-superconducting BLH1, the increase of $1/^{23}T_1$ at high temperatures is similar to that for the non-hydrate $\text{Na}_{0.7}\text{CoO}_2$ [11]. After Gavilano *et al.* [11], the rapid increase of $1/^{23}T_1$ above 200 K can be attributed to the motion of the Na ions. The power-law decrease $T^{0.7}$ of $1/^{23}T_1$ at low temperatures (shown below) agrees with that for the non-hydrate $\text{Na}_{0.7}\text{CoO}_2$ [10].

Figure 5 shows the log-log plots of $1/^{23}T_1$ against temperature for the non-hydrated $\text{Na}_{0.7}\text{CoO}_2$, which are reproduced from Ref. [10,11], and for the bilayer hydrated BLH1 and BLH2. In all the plots, non-Korringa law is observed. As indicated by the solid lines in Fig. 5, all the $1/^{23}T_1$'s at low temperatures show the power-law behaviors of T^n with $n \sim 0.7$ and 0.6 for BLH1 and BLH2, respectively. The magnitude of $1/^{23}T_1$ significantly decreases from the non-hydrated to the bilayer hydrated samples. The water intercalation causes the shielding effect on the Co-to-Na transferred hyperfine coupling as mentioned above.

Figure 6 shows the log-log plot of $1/^{23}T_1$ against temperature for the parent $\text{Na}_{0.7}\text{CoO}_2$ and the non-superconductor BLH1. The magnitude is different with

each other but the temperature dependence is nearly the same in a whole temperature region. The ratio of $1/^{23}\text{T}_1$ of $\text{Na}_{0.7}\text{CoO}_2$ to that of BLH1 is ~ 45 below 10 K. In general, $1/^{23}\text{T}_1$ is expressed by $\propto H_{\text{hf}}^2 S(\omega_n)$ with the hyperfine coupling constant H_{hf} and a spin-fluctuation spectrum $S(\omega_n)$ at an NMR frequency $2\pi\omega_n$ [17]. The difference in the magnitude of $1/^{23}\text{T}_1$ can be ascribed to that in H_{hf} , whose ratio is about 6.6 below 10 K. Thus, the spin dynamics, $S(\omega_n)$, at the Na site of the non-superconducting BLH1 is similar to that of the non-hydrated $\text{Na}_{0.7}\text{CoO}_2$. The *A*-type spin fluctuations, i.e. intra-plane ferromagnetic and inter-plane antiferromagnetic fluctuations, are observed in the non-hydrated $\text{Na}_{0.7}\text{CoO}_2$ [8]. The intercalated water molecules may cut the inter-plane antiferromagnetic couplings. Nearly ferromagnetic intra-plane spin fluctuations persist in the *bilayer* hydrates.

In conclusion, the intercalated water molecules act as the shielding effect on the Co-to-Na magnetic and electric coupling. The spin fluctuations of the *bilayer* hydrated non-superconductor are similar to the *A*-type spin fluctuations of the non-hydrated $\text{Na}_{0.7}\text{CoO}_2$. The superconductivity appears close to the *A*-type magnetic instability.

ACKNOWLEDGMENTS

We thank Mr. T. Waki and Dr. M. Kato for their experimental supports, and Dr. K. Ishida for fruitful discussions. This paper is supported in part by Grants-in Aid for Scientific Research from Japan Society for the Promotion of Science (16076210).

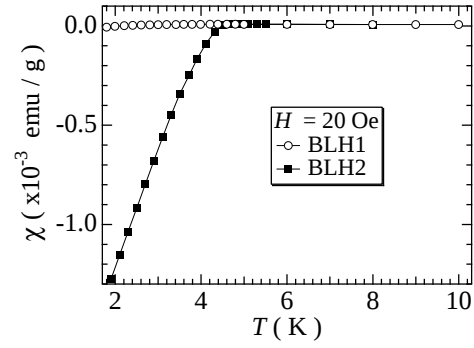


FIG. 1. Temperature dependence of χ of the *bilayer* hydrated BLH1 and BLH2 after cooling in zero magnetic field. T_c of BLH2 is ~ 4.5 K, but that of BLH1 is < 1.8 K.

- J. Paglione, M. Sutherland, R. W. Hill, C. H. Wang and X.H. Chen, Phys. Rev. Lett. **93**, 056401 (2004).
- [10] Y. Ihara, K. Ishida, C. Michioka, M. Kato, K. Yoshimura, H. Sakurai and Eiji Takayama-Muromachi, J. Phys. Soc. Jpn. **73**, 2963 (2004).
- [11] J. L. Gavilano, D. Rau, B. Pedrini, J. Hinderer, H. R. Ott, S. M. Kazakov and J. Karpinski, Phys. Rev. B **69**, 100404(R) (2004).
- [12] I. R. Mukhamedshin, H. Alloul, G. Collin and N. Blanchard, Phys. Rev. Lett. **93**, 167601 (2004).
- [13] Y. Ihara, K. Ishida, C. Michioka, M. Kato, K. Yoshimura, K. Takada, T. Sasaki, H. Sakurai and E. Takayama-Muromachi, J. Phys. Soc. Jpn. **75**, 867 (2005).
- [14] Now preparing a report about the duration effect for the chemical treatment and analysis.
- [15] H. Sakurai, K. Takada, S. Yoshii, T. Sasaki, K. Kindo and E. Takayama-Muromachi, Phys. Rev. B **68**, 132507 (2003).
- [16] M. R. MacHenry, B. G. Silbernagel and J. H. Wernick, Phys. Rev. Lett. **27**, 426 (1971), Phys. Rev. **5**, 2958 (1972).
- [17] T. Moriya, Prog. Theor. Phys. **16**, 33 (1956).

- [1] K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian and T. Sasaki, Nature **422**, 53 (2003).
- [2] P. W. Anderson, Mat. Res. Bull. **8**, 153 (1973).
- [3] G. Baskaran, Phys. Rev. Lett. **91**, 097003 (2003).
- [4] I. Terasaki, Y. Sasago and K. Uchinokura, Phys. Rev. B **56**, R12685 (1997).
- [5] R. E. Schaak, T. Klimczuk, M. L. Foo and R. J. Cava, Nature **424**, 527 (2003).
- [6] H. W. Zandbergen, M. Foo, Q. Xu, V. Kumar and R.J. Cava, Phys. Rev. B **70**, 024101 (2004).
- [7] K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian and T. Sasaki, Solid State Chem. **177**, 372 (2004).
- [8] A. T. Boothroyd, R. Coldea, D. A. Tennant, D. Prabhakaran, L. M. Helme and C. D. Frost, Phys. Rev. Lett. **92**, 197201 (2004).
- [9] S. Y. Li, L. Taillefer, D. G. Hawthorn, M. A. Tanatar,

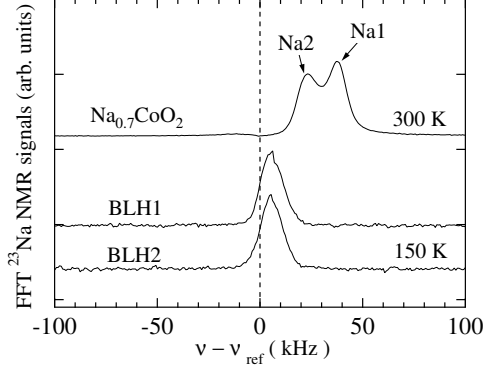


FIG. 2. Fast Fourier transformed ^{23}Na NMR frequency spectra of a parent $\text{Na}_{0.7}\text{CoO}_2$, bilayer hydrated BLH1 and BLH2. The zero shift indicated by the dashed line is $\nu_{\text{ref}} = 75.2542$ MHz ($\nu_{\text{ref}} = \gamma_n H$ with $\gamma_n = 10.054$ MHz/T and $H \sim 7.485$ T), referred to the ^{23}Na NMR line of NaCl in water at 300 K.

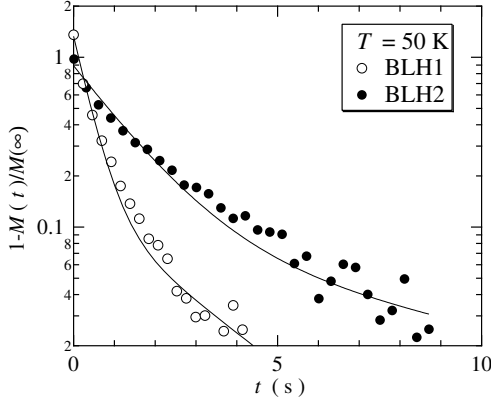


FIG. 3. ^{23}Na nuclear spin-lattice relaxation curves (recovery curves) for bilayer hydrated BLH1 and BLH2 at 50 K. The solid curves are the least-squares fits by theoretical curves (see text) for central transition lines ($I_z = 1/2 \leftrightarrow -1/2$).

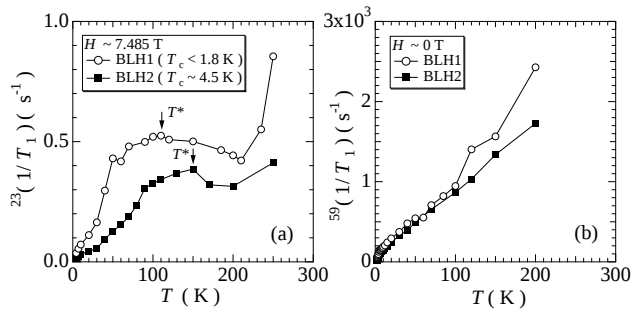


FIG. 4. (a) Temperature dependence of the ^{23}Na nuclear spin-lattice relaxation rate $1/^{23}T_1$ for BLH1 and BLH2. (b) Temperature dependence of the ^{59}Co nuclear spin-lattice relaxation rate $1/^{59}T_1$ for BLH1 and BLH2.

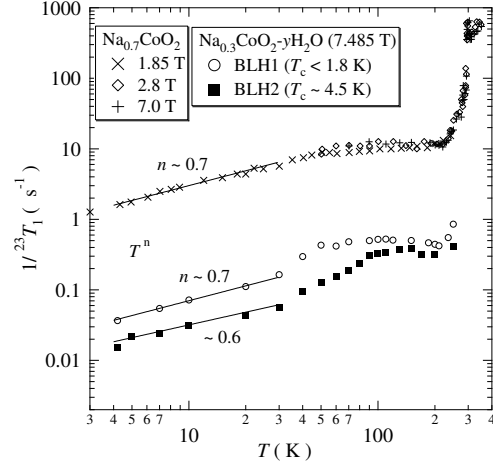


FIG. 5. Log-log plots of ^{23}Na nuclear spin-lattice rate $1/^{23}T_1$ against temperature for the non-hydrated $\text{Na}_{0.7}\text{CoO}_2$, which are reproduced from Ref. [10, 11], the bilayer hydrated $\text{Na}_{0.35}\text{CoO}_2 \cdot 1.3\text{H}_2\text{O}$, BLH1 and BLH2. The solid lines are fits to the low temperature $1/^{23}T_1$ by the power laws of T^n .

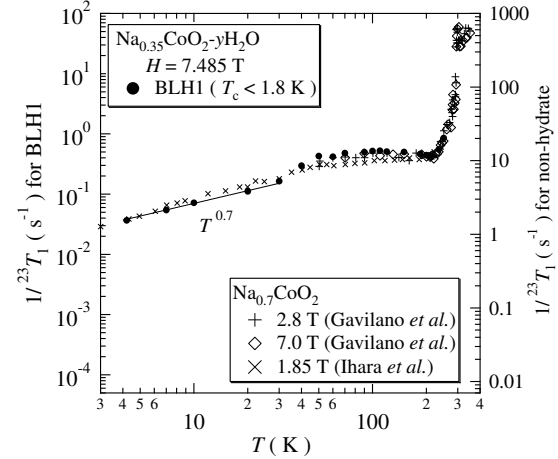


FIG. 6. Temperature dependence of the ^{23}Na nuclear spin-lattice relaxation rate $1/^{23}T_1$ for the parent $\text{Na}_{0.7}\text{CoO}_2$ and the bilayer hydrated non-superconductor BLH1.